


## BRANDS USED ON WOOD PRODUCTS TYPICAL IDENTIFICATION BRAND & KEY <sup>1</sup>

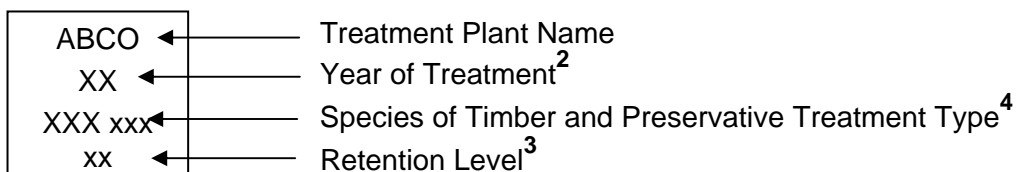

### Preservative Treatment Type

C-Creosote  
PA-Pentachlorophenol in Petroleum  
PC-Pentachlorophenol in Lt. Hydrocarbon Solvent  
SZ-Ammoniacal Copper Zinc Arsenate (ACZA)  
SC-Chromated Copper Arsenate (CCA – A)  
SJ-Chromated Copper Arsenate (CCA – B)  
SK-Chromated Copper Arsenate (CCA – C)  
B-Copper Naphthenate in creosote  
N-Copper Naphthenate in petroleum

### Species

DF-Douglas Fir  
SP-Southern (Yellow) Pine  
JP-Jack Pine  
LP-Lodgepole Pine  
NP-Red Pine  
WP-Ponderosa Pine

} **Round Fence Posts ONLY**

### Retention Level

Minimum Retention of Preservative pcf (Kg/m<sup>3</sup>)

Material and Usage	Creosote	Penta	Copper Naph.	ACZA	CCA (SYP only)	AWPA Use Category
Lumber and Timber	AWPA U1	AWPA U1	AWPA U1	AWPA U1	AWPA U1	AWPA U1
PILES: Southern Yellow Pine	12 (192) SYP	-	0.10 (1.6)	-	-	UC4C-E
Douglas Fir	17 (272) DF	-	0.14 (2.2)	-	-	
Post, Fence, Guide, Sign (Round)	-	0.4 (6.4)	0.055 (0.88)	0.4 (6.4)	0.4 (6.4)	UC4A-B
Post, Fence, Guide, Sign (Sawed)	■	0.5 (8.0)	0.060 (0.96)	0.4 (6.4)	0.4 (6.4)	UC4A-A-4.3
Post, Guardrail, Spacer Blocks (Sawed)	■	0.6 (9.6)	0.075 (1.2)	0.5 (8.0)	0.5 (8.0)	UC4A-A-4.3

<sup>1</sup> This information may be placed on the material by heat branding, hammer stamping or metal tagged in any order. For material treated with waterborne preservatives, the identification mark may be ink stamped, provided the information is clearly visible and legible.

<sup>2</sup> May also include month as in "10-04."

<sup>3</sup> Retention shall be determined by assay. Place letter "A" after number.

<sup>4</sup> Full names or abbreviations shown or trade names may be used for preservatives instead of the recommended standard symbol if desired.