


**BRANDS USED ON WOOD PRODUCTS
TYPICAL IDENTIFICATION BRAND & KEY ¹**

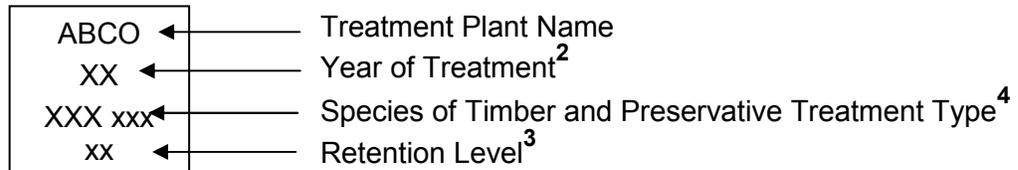

Preservative Treatment Type

- C-Creosote
- PA-Pentachlorophenol in Petroleum
- PC-Pentachlorophenol in Lt. Hydrocarbon Solvent
- SB-Ammoniacal Copper Arsenate (ACA)
- SZ-Ammoniacal Copper Zinc Arsenate (ACZA)
- SC-Chromated Copper Arsenate (CCA – A)
- SJ-Chromated Copper Arsenate (CCA – B)
- SK-Chromated Copper Arsenate (CCA – C)
- B-Copper Naphthenate in creosote
- N-Copper Naphthenate in petroleum

Species

- DF-Douglas Fir
 - SP-Southern (Yellow) Pine
 - JP-Jack Pine
 - LP-Lodgepole Pine
 - NP-Red Pine
 - WP-Ponderosa Pine
- } **Round Fence Posts ONLY**

Retention Level

Minimum Retention of Preservative pcf (Kg/m³)

Material and Usage	Creosote	Penta	Copper Naph.	ACA	ACZA	CCA (SYP only)	AWPA C Standard
Lumber and Timber	12 (192)	0.6 (9.6)	0.075 (1.2)	0.6 (9.6)	0.6 (9.6)	0.6 (9.6)	C2, C14
PILES: Southern Yellow Pine	12 (192) SYP	-	-	-	-	-	C3, C14
Douglas Fir	17 (192) DF	-	-	-	-	-	C3, C14
Post, Fence, Guide, Sign (Round)	8 (128)	0.4 (6.4)	0.055 (0.88)	0.4 (6.4)	0.4 (6.4)	0.4 (6.4)	C5, C14
Post, Fence, Guide, Sign (Sawed)	10 (160)	0.5 (8.0)	0.060 (0.96)	0.4 (6.4)	0.4 (6.4)	0.4 (6.4)	C2, C14
Post, Guardrail, Spacer Blocks (Sawed)	12 (192.2)	0.6 (9.6)	0.075 (1.2)	0.5 (8.0)	0.5 (8.0)	0.5 (8.0)	C2, C14

¹ This information may be placed on the material by heat branding, hammer stamping or metal tagged in any order. For material treated with waterborne preservatives, the identification mark may be ink stamped, provided the information is clearly visible and legible.

² May also include month as in "10-04."

³ Retention shall be determined by assay. Place letter "A" after number.

⁴ Full names or abbreviations shown or trade names may be used for preservatives instead of the recommended standard symbol if desired.