




GENERAL REWRITE. - PLEASE READ CAREFULLY.

ASPHALTIC EQUATIONS & EXAMPLE CALCULATIONS

SCOPE

This IM describes the equations associated with asphaltic materials. In addition, there are a number of example calculations showing how to determine various properties.

NAMING CONVENTION

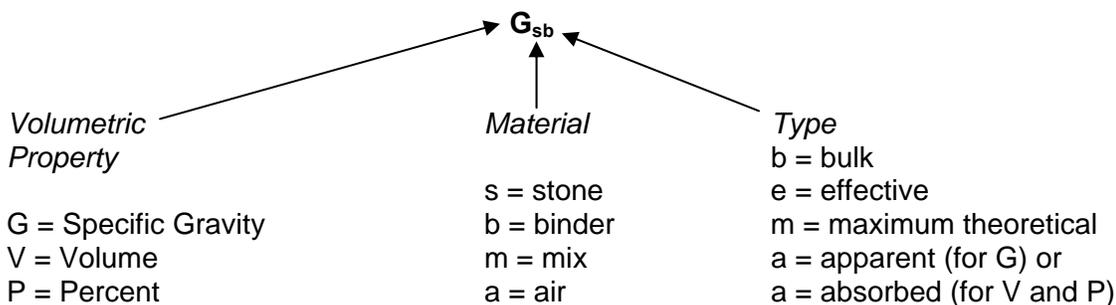

DEFINITIONS

- P_a = % of air voids in compacted hot mix asphalt mixture (percent of total volume) **Lab Voids** for gyratory specimens or **Field Voids** for cores
- P_b = % of asphalt binder in the hot mix asphalt mixture
- $P_{b(RAP)}$ = % of asphalt binder in RAP material
- $P_{b(add)}$ = % of virgin asphalt binder needed to add to the mix to achieve the total intended binder content
- $P_{b(added)}$ = % of virgin asphalt binder in the hot mix asphalt mixture. Does not include the asphalt binder from the RAP
- P_s = % of combined aggregate in the hot mix asphalt mixture
= $100 - P_b$
- P_{ba} = % of asphalt binder absorbed by aggregate, aggregate basis
- P_{be} = effective asphalt binder, %, mixture basis
- % **Abs** = % water absorption of the individual or combined aggregate

ABS	=	fraction of water absorption of the individual or combined aggregate = % Abs/100 ABS is always used in the calculations rather than % Abs.
G_{sa}	=	apparent specific gravity of the aggregate
G_{se}	=	effective specific gravity of the combined aggregate
G_{sb}	=	bulk specific gravity of the aggregate (dry basis)
G_{sb(SSD)}	=	bulk specific gravity of the aggregate (SSD basis) Used for Portland Cement Concrete NOT ASPHALT!!!
G_b	=	specific gravity of the asphalt binder at 25°C (77°F)
G_{mm}	=	maximum specific gravity of the hot mix asphalt mixture. Often referred to as the Rice specific gravity, solid specific gravity or solid density.
G_{mb}	=	bulk specific gravity of compacted hot mix asphalt mixture
G_{mb(measured)}	=	G _{mb} of gyratory specimen as determined from test procedure in IM 321
G_{mb(corrected)}	=	corrected G _{mb} of gyratory specimen at N _{des} , also called Lab Density . G _{mb(corrected)} and G _{mb(measured)} will be the same when compacting to N _{des} so no correction is necessary.
G_{mb(field core)}	=	bulk specific gravity of pavement cores (also G_{mb(field)} or Field Density)
VMA	=	% voids in mineral aggregate, (percent of bulk volume), compacted mix
V_t	=	design target air voids, %
VFA	=	% voids filled with asphalt binder
N_{ini}	=	Number of gyrations used to measure initial compaction.
N_{des}	=	Number of gyrations used to measure design compaction. G _{mb} for Lab Density is determined at N _{des} .
N_{max}	=	Number of gyrations used to measure maximum compaction.
N_x	=	Level of compaction, where x is the number of gyrations.
R	=	temperature correction multiplier obtained from IM 350 Table 2 App. A
d_t	=	density of water at test temperature, g/cc

h_{\max}	=	the height of the specimen at N_{\max} , mm
h_{des}	=	the height of the specimen at N_{des} , mm
h_x	=	the height of the specimen at any gyration level N_x , mm
C_x	=	percent of compaction expressed as a percentage of G_{mm} Where x is the number of gyrations (this is normally N_{ini} or N_{\max})
S	=	slope of the compaction curve
FT	=	Film Thickness, microns
SA	=	Surface Area, m^2/kg
F/B	=	Filler/Bitumen Ratio also called Fines/Bitumen Ratio
σ_{n-1}	=	Sample Standard Deviation
\bar{x}	=	sample average

FORMULAS

All calculations shown have been rounded for ease of presentation. Normally calculations will involve maintaining more significant figures throughout the intermediate calculations and only rounding the final result. The values generated by the software specified by the DOT will be the accepted results for reporting purposes.

All specific gravity calculations will be reported to 3 decimal places. Binder content is reported to 2 decimal places. Percent voids, VMA and VFA are reported to 1 decimal place.

Unless noted as otherwise, the following information is given to perform the calculations. Any additional needed information will be provided with the sample calculation.

$P_b = 5.75\%$	$G_{\text{sa}} = 2.667$	$G_{\text{mb (field)}} = 2.215$
$P_s = 100 - 5.75 = 94.25\%$	$G_{\text{se}} = 2.659$	$G_{\text{mb (measured)}} = 2.310$
$\% \text{ Abs} = 1.39$	$G_{\text{sb}} = 2.572$	$G_{\text{mb (corrected)}} = 2.273$
$\text{ABS} = 1.39/100 = 0.0139$	$G_{\text{sb(SSD)}} = 2.608$	$\% \text{ RAP} = 10.0\%$
$G_b = 1.031$	$G_{\text{mm}} = 2.438$	$P_{\text{b(RAP)}} = 5.00\%$
$\% \text{ minus \#200 (75 } \mu\text{m) sieve} = 5.0\%$		

VOLUMETRIC EQUATIONS

To convert the specific gravity of asphalt binder from one temperature to another, the following two equations are used.

$$G_b \text{ (at 60°F)} = \frac{G_b \text{ (at 77°F)}}{0.9961} = \frac{1.031}{0.9961} = 1.035$$

$$G_b \text{ (at 77°F)} = 0.9961 \times G_b \text{ (at 60°F)} = 0.9961 \times (1.035) = 1.031$$

$$\begin{aligned} \% \text{ Abs} &= \frac{W_a + W_b - W_c}{W_c} \times 100 \\ &= \frac{1315.7 + 690.3 - 2000.0}{2000.0} \times 100 = 0.30\% \end{aligned}$$

Where: W_a = Saturated-Surface-Dry (SSD) weight of coarse portion, 1315.7 g
 W_b = Saturated-Surface-Dry (SSD) weight of fine portion, 690.3 g
 W_c = Combined dry weight of coarse and fine portion, 2000.0 g

$$\begin{aligned} \% \text{ Abs}_{(\text{combined})} &= [\% \text{ Abs}_1 \times (P_{s1})] + [\% \text{ Abs}_2 \times (P_{s2})] + [\% \text{ Abs}_3 \times (P_{s3})] + \dots \\ &= 0.67(0.50) + 1.23(0.05) + 2.21(0.45) = 1.39\% \end{aligned}$$

Where: $\% \text{ Abs}_1 = 0.67\%$ $P_{s1} = 50\%$
 $\% \text{ Abs}_2 = 1.23\%$ $P_{s2} = 5\%$
 $\% \text{ Abs}_3 = 2.21\%$ $P_{s3} = 45\%$

$$G_{sa} = \frac{W \times R}{W + W_1 - W_2} = \frac{(2000.0)(1.0000)}{2000.0 + 6048.0 - 7298.1} = 2.667$$

Where: W = Weight of dry sample, 2000.0 g
 W_1 = Sample weight of pycnometer filled with water at test temperature, 6048.0 g
 W_2 = Sample weight of pycnometer filled with water and sample, 7298.1 g
 R = Multiplier to correct temperature to 77°F = 1.0000 @ 77°F

$$G_{sb} = \frac{G_{sa}}{1 + (\text{ABS}) \times (G_{sa})} = \frac{2.667}{1 + (0.0139)(2.667)} = 2.572$$

$$G_{sb \text{ (combined)}} = \frac{100}{\frac{P_{s1}}{G_{sb1}} + \frac{P_{s2}}{G_{sb2}} + \frac{P_{s3}}{G_{sb3}} + \dots} = \frac{100}{\frac{50.0}{2.657} + \frac{5.0}{2.642} + \frac{45.0}{2.640}} = 2.649$$

Where: $P_{s1} = 50.0\%$ $G_{sb1} = 2.657$
 $P_{s2} = 5.0\%$ $G_{sb2} = 2.642$
 $P_{s3} = 45.0\%$ $G_{sb3} = 2.640$

$$G_{se} = \frac{P_s}{\frac{100}{G_{mm}} - \frac{P_b}{G_b}} = \frac{100 - 5.75}{\frac{100}{2.438} - \frac{5.75}{1.031}} = 2.659$$

$$G_{mm} = \frac{W \times R}{W + W_1 - W_2} = \frac{(2020.0)(1.0000)}{2020.0 + 6048.0 - 7239.5} = 2.438$$

Where: W = Sample weight of sample, 2020.0 g
 W_1 = Sample weight of pycnometer filled w/water at test temperature, 6048.0 g
 W_2 = Sample weight of pycnometer filled w/water and sample, 7239.5 g
 R = Multiplier to correct temperature to 77°F = 1.0000 @ 77°F

To correct the density of water to 77°F the R multiplier is used. The value of R is given in the tables in [IM's 350](#) and [380](#) for temperatures from 60 to 130°F. R is calculated as follows:

$$R = \frac{d_t}{0.99707} = \frac{0.99707}{0.99707} = 1.0000$$

Where: d_t = density of water at temperature t = 0.99707 g/cc at 77°F.

$$G_{mb} \text{ (or } G_{mb \text{ (measured)}}) = \frac{W_1}{W_3 - W_2} = \frac{4800.0}{4805.6 - 2727.7} = 2.310$$

Where: W_1 = Sample Dry weight, 4800.0 g
 W_2 = Sample weight in water, 2727.7 g
 W_3 = Sample weight in air, SSD, 4805.6 g

$$P_a \text{ (lab voids)} = \frac{G_{mm} - G_{mb}}{G_{mm}} \times 100 = \frac{2.438 - 2.310}{2.438} \times 100 = 5.3\%$$

%G_{mm} (field core)	$= \frac{G_{mb(\text{field core})}}{G_{mm(\text{lot avg.})}} \times 100$	$= \frac{2.215}{2.438} \times 100 = 90.9\%$
P_a (field voids)	$= 100 - \%G_{mm}$	$= 100 - 90.9 = 9.1\%$
VMA	$= 100 - \left[\frac{G_{mb} \times P_s}{G_{sb}} \right]$	$= 100 - \frac{(2.310)(94.25)}{2.572} = 15.4\%$
VFA	$= \frac{VMA - P_a}{VMA} \times 100$	$= \frac{15.4 - 5.3}{15.4} \times 100 = 65.6\%$
P_{ba}	$= \frac{(G_{se} - G_{sb})}{(G_{se} \times G_{sb})} \times G_b \times 100$	$= \frac{2.659 - 2.572}{(2.659)(2.572)} \times 1.031 \times 100 = 1.31\%$
P_{be}	$= P_b - \left[\frac{P_{ba} \times P_s}{100} \right]$	$= 5.75 - \frac{(1.31)(94.25)}{100} = 4.52\%$
F/B (fines/bitumen)	$= \frac{\text{Total \% of minus \#200 material}}{P_{be}}$	$= \frac{5.00}{4.52} = 1.11$

Where: Total % of minus #200 (75 μm) includes both virgin aggregate and RAP when used.

GYRATORY EQUATIONS

If compacting to N_{max} a correction to the measured G_{mb} must be performed. The corrected G_{mb} ($G_{mb \text{ (corrected)}}$) is then used in the calculations for P_a (lab voids) and **VMA**.

To correct G_{mb} from the measured value at N_{max} to the corrected value at N_{des} :

$$G_{mb \text{ (corrected)}} \quad (\text{lab density}) = (G_{mb \text{ (measured)}}) \times \frac{h_{max}}{h_{des}} = (2.310) \frac{117.5}{119.4} = 2.273$$

Where: $h_{max} = 117.5$ mm (the height at N_{max}) and $h_{des} = 119.4$ (the height at N_{des})

To find the percent of maximum specific gravity ($\%G_{mm}$) at a specific gyration (N_x):

$$C_x \quad (\%G_{mm}) = \frac{(G_{mb \text{ (measured)}}) \times (h_{max})}{(G_{mm}) \times (h_x)} \times 100$$

Given: $N_{ini} = 8$ gyrations $h_8 = 135.4$ mm
 $N_{des} = 109$ gyrations $h_{109} = 119.4$ mm
 $N_{max} = 174$ gyrations $h_{174} = 117.5$ mm

$$C_8 = \left(\frac{(2.310) \times (117.5 \text{ mm})}{(2.438) \times (135.4 \text{ mm})} \right) \times 100 = 82.2\%$$

$$C_{109} = \left(\frac{(2.310) \times (117.5 \text{ mm})}{(2.438) \times (119.4 \text{ mm})} \right) \times 100 = 93.2\%$$

$$C_{174} = \left(\frac{(2.310) \times (117.5 \text{ mm})}{(2.438) \times (117.5 \text{ mm})} \right) \times 100 = 94.7\%$$

To find the slope of the gyratory compaction curve:

$$S = \frac{(\log(N_{max}) - \log(N_{ini}))}{C_{max} - C_{ini}} = \frac{(\log(174) - \log(8))}{0.947 - 0.822} = 10.7$$

Where: C_{max} and C_{ini} are expressed as decimals.

RAP FORMULAS

To determine the percent of asphalt binder to add to a mix containing RAP ($P_{b(\text{add})}$) to achieve the total intended P_b shown on the JMF (this the value to which the plant controls are set):

$$P_{b(\text{add})} = \frac{[(100) \times (\text{total intended } P_b)] - [(\% \text{ RAP}) \times (P_{b(\text{RAP})})]}{100 - [(\% \text{ RAP}) \times (P_{b(\text{RAP})}) \times (0.01)]}$$

$$= \frac{(100)(5.75) - (10.0)(5.00)}{100 - (10.0)(5.00)(0.01)} = 5.28\%$$

To determine the percent of aggregate contributed by the RAP in the total aggregate blend:

$$\% \text{ RAP}_{(\text{aggregate})} = \frac{(\% \text{ RAP}) \times [1.00 - (P_{b(\text{RAP})} \times 0.01)]}{\% \text{ virgin agg.} + [(\% \text{ RAP}) \times (1.00 - (P_{b(\text{RAP})} \times 0.01))]} \times 100$$

$$= \frac{(10.0)(1.00 - (5.00)(0.01))}{90.0 + (10.0)(1.00 - (5.00)(0.01))} \times 100 = 9.55\%$$

To determine the actual percent virgin aggregate in the total aggregate blend containing RAP:

$$\% \text{ virgin agg.} = \frac{\% \text{ virgin agg.}}{\% \text{ virgin agg.} + [(\% \text{ RAP}) \times (1.00 - (P_{b(\text{RAP})} \times 0.01))]} \times 100$$

$$= \frac{90.0}{90.0 + (10.0)(1.00 - (5.00)(0.01))} \times 100 = 90.45\%$$

To determine the total percent asphalt binder in a mix containing RAP:

$$\text{Total } P_b = P_{b(\text{added})} + [(\% \text{ RAP}) \times (P_{b(\text{RAP})}) \times (0.01)] - [(P_{b(\text{added})}) \times (\% \text{ RAP}) \times (P_{b(\text{RAP})}) \times (0.0001)]$$

$$= 5.28 + (10.0)(5.00)(0.01) - (5.28)(10.0)(5.00)(0.0001) = 5.75\%$$

Where: $P_{b(\text{added})}$ is the actual percent of virgin asphalt binder added to the mix from the tank stick, flow meter or batch weights - **not the $P_{b(\text{add})}$ determined above which is the original determination on the JMF.**

FRICITION AGGREGATE CALCULATIONS

Percent Retained on #4 Sieve:

$$\% \text{ +\#4 Frictional aggregate} = \frac{(\% \text{ frictional agg. retained on \#4}) \times (\% \text{ frictional agg. in total blend})}{(\% \text{ retained on \#4 of total blend})}$$

Example: The aggregate blend contains 20% quartzite as the Type 2 friction class aggregate, the quartzite gradation shows 90% **retained** on the #4 sieve, and the combined gradation of the blend shows 60% **retained** on the #4 sieve:

$$\% \text{ +\#4 frictional aggr. in total blend} = \text{+\#4 Type 2} = \frac{(90)(20)}{60} = 30\%$$

Percent Passing the #4 Sieve:

$$\% \text{ -\#4 Type 2 aggregate} = \frac{(\% \text{ passing \#4 of Type 2 aggr.}) \times (\% \text{ Type 2 aggr. in total blend})}{(\% \text{ passing \#4 of total blend})}$$

Example: For a single Type 2 aggregate:
Quartzite Type 2 aggregate is 20% of the total blend and has 58% passing the #4 sieve.
The combined gradation of the total blend has 65% passing the #4 sieve.

$$\% \text{ -\#4 Type 2 in the total blend} = \frac{(58) \times (20)}{65} = 17.8\%$$

If more than one Type 2 aggregate is included in the blend the gradations of the Type 2 aggregates must be combined first in the numerator to determine the percent passing the #4 sieve for the Type 2 aggregate as shown in the following example.

Example: For multiple Type 2 aggregates:
Three quartzite aggregates are included in the total blend. The graded quartzite aggregate is 20% of the total blend and has 58% passing the #4 sieve. The quartzite man sand is 10% of the total blend and has 100% passing the #4 sieve. The quartzite chip is 5% of the total blend and has 5% passing the #4 sieve. The combined gradation of the total blend has 65% passing the #4 sieve.

The % Type 2 in the total blend combined -#4 is:

$$\% \text{ -\#4 Type 2 in the total blend} = \frac{[(58 \times 20) + (100 \times 10) + (5 \times 5)]}{65} = 33.6\%$$

Fineness Modulus

The fineness modulus of the Type 2 (FM_{Type2}) material is expressed as 600 minus the total of the percents passing each of the six sieves from the #4 to the #100 sieves divided by 100 and then multiplied by the percentage of Type 2 aggregate in the total blend expressed as a decimal.

$$FM_{Type2} = \frac{[600 - (P_4 + P_8 + P_{16} + P_{30} + P_{50} + P_{100})]}{100} \times P_{Type2}$$

Where:

P_x is the percent passing sieve #x (x = #4, #8, #16, #30, #50, and #100)

P_{Type 2} is the percent of Type 2 aggregate in the total blend expressed as a decimal

When more than one Type 2 aggregate is included in the total blend the gradations of the Type 2 aggregates must be combined first to determine the percent passing each of the six sieves for the total Type 2 aggregate as shown in the following example.

Example:

Given: The following gradations of the three Type 2 aggregates and the percentages in the total blend:

Percent Passing	3/4	1/2	3/8	#4	#8	#16	#30	#50	#100	#200
20% Graded Quartzite	100	98	78	58	48	38	28	18	8.0	4.0
10% Quartzite Man Sand				100	75	52	33	22	7.0	2.0
5% Quartzite Chip	100	95	35	5.0	4.5	4.0	3.5	3.0	2.0	1.0

The total percent Type 2 quartzite in the total blend is 20+10+5=35%

To combine the gradations of the Type 2 aggregates, multiply the percent passing each sieve (#4 to #100) for each aggregate by the percent of that aggregate in the total blend, sum the results individually for each sieve then divide the sum by the total percent Type 2 in the total blend as shown below. Express the result to two significant figures.

Combined gradation of the Type 2 for the #4 sieve: $= \frac{(58 \times 20) + (100 \times 10) + (5 \times 5)}{35} = 62$

Perform this same calculation for each of the other five sieves, #8, #16, #30, #50 and #100

Percent Passing	3/4	1/2	3/8	#4	#8	#16	#30	#50	#100	#200
Total Type 2 Combined				62	50	37	26	17	6.9	

$$FM_{\text{Type2}} = \frac{[600 - (62 + 50 + 37 + 26 + 17 + 6.9)]}{100} \times 0.35 = 1.40$$

FILM THICKNESS EXAMPLE:

SIEVE ANALYSIS % PASSING													
Sieve	in. (mm)	1 (25.0)	3/4 (19.0)	1/2 (12.5)	3/8 (9.5)	#4 (4.75)	#8 (2.36)	#16 (1.18)	#30 (0.600)	#50 (0.300)	#100 (0.150)	#200 (0.075)	
Combined Grading		100	100	95	86	68	47	38	26	10	5.4	3.9	
Surface Area Coefficient						0.0041	0.0082	0.0164	0.0287	0.0614	0.1229	0.3277	TOTAL
Surface Area (m ² /kg)		0.41				0.28	0.39	0.62	0.75	0.61	0.66	1.28	5.00

The surface area (**SA**) is found by taking the % Passing times the Surface Area Coefficient. The Surface Area for the material above the #4 sieve is a constant 0.41. The total surface area is found by adding all of the individual surface area values.

$$\begin{aligned} \text{SA} \quad (\text{for each sieve}) &= (\% \text{ Passing}) \times (\text{Surface Area Coefficient}) \\ &= (38)(0.0164) = 0.62 \quad (\text{for the \#16 sieve above}) \end{aligned}$$

Where: The Surface Area Coefficients are constants.

$$\text{FT} \quad (\text{Film Thickness}) = \frac{P_{be}}{\text{SA}} \times 10 = \frac{4.52}{5.00} \times 10 = 9.0$$

MISCELLANEOUS

$$\text{Optimum } P_b = \frac{(\text{high voids} - \text{target voids})}{(\text{high voids} - \text{low voids})} \times (\text{high } P_b - \text{low } P_b) + \text{low } P_b$$

Where: Target voids = 4.0

	P_b	P_a	
(low P_b =)	4.75	5.5	(= high voids)
(high P_b =)	5.75	3.0	(= low voids)
	6.75	1.2	

Since the target voids of 4.0% falls between 5.5 and 3.0 they are the high voids and low voids respectively. The asphalt contents associated with those voids are used as the low P_b and high P_b respectively.

$$= \frac{(5.5 - 4.0)}{(5.5 - 3.0)} \times (5.75 - 4.75) + 4.75 = 5.35\%$$

$$\% \text{ Moisture} = \frac{\text{Wet Wt. Sample} - \text{Dry Wt. Sample}}{\text{Dry Wt. Sample}} \times 100$$

Where: Wet Wt. Sample = 2100.0 g
 Dry Wt. Sample = 2000.0 g

$$= \frac{2100.0 - 2000.0}{2000.0} \times 100 = 5.0\%$$

To adjust the height of a G_{mb} specimen to reach the intended height, the following equation is used.

$$\text{Adjusted sample weight} = \frac{(\text{trial sample weight}) \times (\text{intended height})}{\text{trial sample height}}$$

$$= \frac{(4775.0)(115.0)}{109.5} = 5014.8$$

$$G_{sb} \quad (\text{from } G_{sb(SSD)}) = \frac{G_{sb(SSD)}}{1 + \text{ABS}} = \frac{2.608}{1 + 0.0139} = 2.572$$

$$\text{Percent of Lab Density} = \frac{G_{mb(\text{field core})}}{G_{mb}} \times 100 = \frac{2.215}{2.273} \times 100 = 97.4\%$$

$$\begin{aligned} \text{Min. } P_b &= \frac{[(G_b)(G_{se})(VMA - V_t) + (G_b)(100 - VMA)(G_{se} - G_{sb})]}{(G_b)(G_{se})(VMA - V_t) + (G_b)(100 - VMA)(G_{se} - G_{sb}) + (G_{se})(G_{sb})(100 - VMA)} \times 100 \\ &= \frac{[(1.031)(2.659)(15.4 - 4.0) + (1.031)(100 - 15.4)(2.659 - 2.572)]}{(1.031)(2.659)(15.4 - 4.0) + (1.031)(100 - 15.4)(2.659 - 2.572) + (2.659)(2.572)(100 - 15.4)} \times 100 = 6.29\% \end{aligned}$$

You have 13,000 grams of aggregate and 650 grams of asphalt binder. Determine the asphalt binder content (P_b) of the mixture.

$$P_b = \frac{W_b}{W_s + W_b} \times 100 = \frac{650}{13000 + 650} \times 100 = 4.76\%$$

Where: W_b = Weight of the asphalt binder, g
 W_s = Weight of the aggregate, g
 P_b = Percent binder of the mix, mix basis

You have 13,000 grams of aggregate. You want to prepare a mixture having 5.5% asphalt binder content based on the total mix. Determine the weight of the asphalt binder you need to add to the aggregate.

$$W_b = \frac{(P_b) \times (W_s)}{(P_s)} = \frac{(5.5)(13000)}{100 - (5.5)} = 756.6$$

Where: W_b = Weight of the added binder, mix basis, g
 W_s = Weight of the aggregate, g

QUALITY INDEX (QI) EXAMPLE %G_{mb} Method:

For use on projects not using the PWL specifications

Given: lab. lot average G_{mb(corrected)} = 2.408
field G_{mb} of individual cores: 2.319, 2.316, 2.310, 2.298, 2.242, 2.340, and 2.345.
% of lab density = 94%, 95%, or 96%. For this example 95% is used.

Determine the average field density (G_{mb}) of the seven cores.

$$\bar{x} = \frac{2.319 + 2.316 + 2.310 + 2.298 + 2.242 + 2.340 + 2.345}{7} = 2.310$$

The sample standard deviation is determined as follows:

$$\sigma_{n-1} = \sqrt{\frac{\sum (x - \bar{x})^2}{n - 1}} = \sqrt{\frac{0.007}{7 - 1}} = 0.034$$

Where: x = individual sample value
n = number of samples
 \bar{x} = average of all samples

The Quality Index for density shall be determined according to the following calculation:

$$\text{Q.I. (Density)} = \frac{(\text{Avg. } G_{mb})_{\text{FIELD LOT}} - ((\% \text{ Density})_{\text{SPECIFIED}} \times (\text{Avg. } G_{mb})_{\text{LAB LOT}})}{(\text{Std. Dev. } G_{mb})_{\text{FIELD LOT}}}$$

$$\text{QI} = \frac{2.310 - (0.95)(2.408)}{0.034} = 0.66$$

The QI is less than 0.72. Check for outliers. To test for a suspected outlier result, apply the appropriate formula.

$$\text{Suspected High Outlier} = \frac{\text{Highest } G_{mb} - \text{Avg. } G_{mb}}{n-1} = \frac{2.345 - 2.310}{0.034} = 1.03$$

$$\text{Suspected Low Outlier} = \frac{\text{Avg. } G_{mb} - \text{Lowest } G_{mb}}{n-1} = \frac{2.310 - 2.242}{0.034} = 1.99$$

The highest density or lowest density shall not be included if the suspected outlier result is more than 1.80 for seven samples. The quality index shall then be recalculated for the remaining six samples.

The suspected low outlier result is greater than 1.80 for seven samples, therefore the core with the lowest density, 2.242, is an outlier.

Recalculate the QI for the remaining six densities (excluding the outlier).

Avg. G_{mb} (field lot)(new) = 2.321 σ_{n-1} (new) = 0.018

$$QI_{(new)} = \frac{2.321 - (0.95)(2.408)}{0.018} = 1.88$$

GRADATION EXAMPLE (Combined Gradation):

Assume the proportions of the individual aggregates are as follows: 50% 3/4" Minus, 5% 3/8" Chips, and 45% Nat. Sand. Then using the following gradations for the individual aggregates, determine the combined gradation.

	% Passing									
Sieve Size	3/4"	1/2"	3/8"	#4	#8	#16	#30	#50	#100	#200
3/4" Minus	100	90	75	43	21	17	15	12	9.8	7.4
3/8" Chip	100	100	70	32	5	1.8	1.5	1.1	0.9	0.7
Nat. Sand	100	100	100	100	80	65	40	9	1.0	0.5
combined	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____

To determine the combined gradation, take each individual material % Passing times the percentage of that material in the blend. For example, take the 50% of the 3/4" Minus material times the % Passing for that material.

$$3/4" \text{ Minus Portion } \% \text{ Passing } \#200 \text{ sieve: } = 7.4 \times \frac{50}{100} = 3.7$$

Do the same thing with each of the other aggregates and sieve sizes to obtain the following:

3/4" Minus	50.0	45.0	37.5	21.5	10.5	8.5	7.5	6.0	4.9	3.7
3/8" Chip	5.0	5.0	3.5	1.6	0.3	0.1	0.1	0.1	0.0	0.0
Nat. Sand	45.0	45.0	45.0	45.0	36.0	29.3	18.0	4.1	0.5	0.2

Next, sum the individual sieve sizes to get the combined gradation. This will result in the following combined gradation.

Combined	100.0	95.0	86.0	68.1	46.8	37.9	25.6	10.2	5.4	3.9
----------	-------	------	------	------	------	------	------	------	-----	-----

BATCHING EXAMPLE:

You have been directed to prepare a 13,000-gram batch of aggregate composed of the aggregates used above with the same proportions. The ¾" Minus has been split into four size fractions by sieving on the 12.5 mm, 9.5 mm and 4.75 mm sieves. The 1" Chip has been split into three size fractions by sieving on the 9.5 mm and 4.75 mm sieves. The Nat. Sand is one size fractions passing the 4.75 mm sieve. Complete the following batching sheet by determining the mass of each aggregate needed, the percentage of each size fraction and the weight of each size fraction.

Weight ¾" Minus @ 50% = _____ grams

Sieve	% Passing	Size Fraction	% In Size Fraction	Weight Needed Each Fraction	Cumulative Weight
19 mm	100				
12.5 mm	90	-19 + 12.5	_____	_____	_____
9.5 mm	75	-12.5 + 9.5	_____	_____	_____
4.75 mm	43	-9.5 + 4.75	_____	_____	_____
		-4.75	_____	_____	_____

Weight 1" Chip @ 5% = _____ grams

Sieve	% Passing	Size Fraction	% In Size Fraction	Weight Needed Each Fraction	Cumulative Weight
12.5 mm	100				
9.5 mm	70	-12.5 + 9.5	_____	_____	_____
4.75 mm	32	-9.5 + 4.75	_____	_____	_____
		-4.75	_____	_____	_____

Weight Nat. Sand @ 45% = _____ grams

Sieve	% Passing	Size Fraction	% In Size Fraction	Weight Needed Each Fraction	Cumulative Weight
4.75 mm	100	-4.75	_____	_____	_____

The weight of each material is found by taking the percentage of the blend each material is times the total batch weight. For example, the weight of the ¾" Minus is found by taking 50% of the 13,000 gram batch, or 6,500 grams.

The % In Size Fraction column is found by subtracting the % Passing from one size by the previous size % Passing. For example, the % In Size Fraction for the -19 + 12.5 Size Fraction

is found by subtracting 90% Passing the 12.5 mm sieve from 100% Passing the 19 mm sieve. This process is repeated for each size fraction. The last line in the % In Size Fraction column is found by adding each of the individual values above it. The total should be 100.0%.

The Weight Needed Each Fraction is found by taking the % In Size Fraction value and multiplying it by the total mass of that aggregate. For example, for the ¾" Minus material, there is 10% in the -19 + 12.5 size fraction. Take this 10% times the mass of 6,500 grams to get the Weight Needed value of 650 grams.

The Cumulative Weight is found by taking the first value in the Weight Needed column and placing it in the first spot for the Cumulative Weight column. For example, there was 650 grams needed in the previous example. This value would go on the first line of the Cumulative Weight column. Each successive line requires adding the corresponding Weight Needed value with the previous Cumulative Weight value. Below are the solutions for the example shown above.

Weight ¾" Minus @ 50% = 6500.0 grams

Sieve	% Passing	Size Fraction	% In Size Fraction	Weight Needed Each Fraction	Cumulative Weight
19 mm	100				
12.5 mm	90	-19 + 12.5	10.0	650.0	650.0
9.5 mm	75	-12.5 + 9.5	15.0	975.0	1625.0
4.75 mm	43	-9.5 + 4.75	32.0	2080.0	3705.0
		-4.75	43.0	2795.0	6500.0
			100.0		

Weight ½" Chip @ 5% = 650.0 grams

Sieve	% Passing	Size Fraction	% In Size Fraction	Weight Needed Each Fraction	Cumulative Weight
12.5 mm	100				
9.5 mm	70	-12.5 + 9.5	30.0	195.0	6695.0
4.75 mm	32	-9.5 + 4.75	38.0	247.0	6942.0
		-4.75	32.0	208.0	7150.0
			100.0		

Weight Nat. Sand @ 45% = 5850.0 grams

Sieve	% Passing	Size Fraction	% In Size Fraction	Weight Needed Each Fraction	Cumulative Weight
4.75 mm	100	-4.75	100.0	5850.0	13000.0
			100.0		

The Cumulative Weight at the end of the batching should always equal the desired total batch weight.

Determination of Tons of Asphalt Binder Used

Determine the tons of asphalt binder used in the mix for a given day using the following information:

Weights of all Binder @ 60°F = 8.67 lbs./gal.
Beginning tank stick 18,000 gal. @ 296°F
28.0 tons Binder hauled in during the day's run
Ending tank stick 16,000 gal. @ 296°F
Volume correction factor for correcting Binder @ 296°F to Binder @ 60°F = 0.9200

The difference between the beginning and ending tank stick readings is the first place to start. There were 2,000 gal. of binder used plus all of the binder hauled in during the day.

To combine these quantities, they must be converted to tons. First the gallons used must be corrected to 60°F. Since the temperature is the same for the beginning and ending tank stick readings the correction can be done on the difference between the two readings. If the temperatures were different for the two readings, the temperature correction would need to be done on the individual readings before the difference is determined.

$$2,000 \text{ gal binder @ } 296^\circ\text{F} = (2000 \text{ gal @ } 296^\circ\text{F}) \times 0.9200 = 1840 \text{ gal @ } 60^\circ\text{F}$$

This value must then be converted to the tons of binder.

$$1840 \text{ gal @ } 60^\circ\text{F} = \frac{(1840 \text{ gal}) \times (8.67 \text{ lbs./gal.})}{2000 \text{ lbs./ton}} = 7.98 \text{ tons}$$

This value in addition to the 28.0 tons of binder hauled in during the day is the amount used in the mix that day.

$$\text{Tons of binder used in mix} = 28.0 \text{ tons} + 7.98 \text{ tons} = 35.98 \text{ tons binder}$$

DETERMINING CORRECTION FACTORS FOR COLD FEED VS. IGNITION OVEN

		Sieve Sizes - Percent Passing												Surface
		1 1/2"	1"	3/4"	1/2"	3/8"	#4	#8	#16	#30	#50	#100	#200	Area
SU4-30D	Ign. Oven	100.0	100.0	99.0	89.0	77.0	47.0	31.0	20.0	14.0	8.6	6.4	5.2	4.60534
4-A	Cold-Feed	100.0	100.0	99.0	89.0	76.0	47.0	29.0	19.0	13.0	7.8	5.6	4.4	4.13424
Correction Factor		0.0	0.0	0.0	0.0	-1.0	0.0	-2.0	-1.0	-1.0	-0.8	-0.8	-0.8	-0.5

The correction factor is determined by taking the percent passing an ignition oven sieve and subtracting it from the percent passing of the corresponding cold-feed sieve. For example, there is 31 percent passing the number #8 sieve for the ignition oven and 29 percent passing the #8 sieve for the cold-feed. The correction factor for this sieve size is -2.0. The correction factor is applied to the ignition oven test results for **I.M. 216** comparison.

This same procedure is used regardless of using a single gradation or multiple gradations to determine the correction factors. If multiple gradations are used, the correction factor is determined for each individual result and the resulting correction factors averaged for each sieve.

QUALITY INDEX (QI) FIELD VOIDS EXAMPLE %G_{mm} Method:

For use on projects using the PWL specifications

Given: Field G_{mb} of individual cores: 2.319, 2.316, 2.310, 2.298, 2.242, 2.340, 2.345, 2.310.
 Lot Average G_{mm} = 2.501

Determine the average field density {(Avg G_{mb})_{(FIELD LOT)}} of the eight cores.

$$\bar{x} = \frac{2.319 + 2.316 + 2.310 + 2.298 + 2.242 + 2.340 + 2.345 + 2.310}{8} = 2.310$$

The sample standard deviation (σ_{n-1}) of G_{mb} for the field lot {(Std. Dev. G_{mb})_{FIELD LOT} } is determined as follows:

$$\sigma_{n-1} = \sqrt{\frac{\sum(x-\bar{x})^2}{n-1}} = \sqrt{\frac{0.007}{8-1}} = 0.032$$

Where: x = individual sample value
 n = number of samples
 \bar{x} = average of all samples

The Lower and Upper Quality Indexes for field voids shall be determined according to the following calculations:

$$QI_U \text{ (Field Voids)} = \frac{(\text{Avg. } G_{mb})_{\text{FIELDLOT}} - (0.915 \times \text{Lot Avg. } G_{mm})}{(\text{Std. Dev. } G_{mb})_{\text{FIELDLOT}}}$$

$$QI_L \text{ (Field Voids)} = \frac{(0.965 \times \text{Lot Avg. } G_{mm}) - (\text{Avg. } G_{mb})_{\text{FIELDLOT}}}{(\text{Std. Dev. } G_{mb})_{\text{FIELDLOT}}}$$

Example:

$$QI_U \text{ (Field Voids)} = \frac{2.310 - (0.915 \times 2.501)}{0.032} = 0.67$$

$$QI_L \text{ (Field Voids)} = \frac{(0.965 \times 2.501) - 2.310}{0.032} = 3.23$$

If the QI produces a PWL that results in less than 100% pay, check for outliers. To test for a suspected outlier result, apply the appropriate formula.

$$\text{Suspected High Outlier} = \frac{\text{Highest } G_{mb} - \text{Avg. } G_{mb}}{n-1} = \frac{2.345 - 2.310}{0.032} = 1.09$$

$$\text{Suspected Low Outlier} = \frac{\text{Avg. } G_{mb} - \text{Lowest } G_{mb}}{n-1} = \frac{2.310 - 2.242}{0.032} = 2.13$$

The highest density or lowest density shall not be included if the suspected outlier result is more than 1.80 for eight samples. The quality index shall then be recalculated for the remaining seven samples.

The suspected low outlier result is greater than 1.80 for eight samples, therefore the core with the lowest density, 2.242, is an outlier.

Recalculate the upper and lower QI for the remaining seven densities (excluding the outlier).

$$\text{Avg. } G_{mb} \text{ (field lot)(new)} = 2.320 \quad \sigma_{n-1} \text{ (new)} = 0.020$$

$$QI_U \text{ (new)} = \frac{2.320 - (0.915) \times (2.501)}{0.020} = 1.58$$

$$QI_L \text{ (new)} = \frac{(0.965) \times (2.501) - 2.320}{0.020} = 4.67$$

DETERMINATION OF PERCENT WITHIN LIMITS (PWL)

Field Voids

Calculate the upper and lower QI for field voids. Using Table 6 in AASHTO R 9-97 Appendix C and the QI value, the PWL can be determined using a sample size of N=8. A sample size of N=8 is always used regardless of the actual number of samples. The program provided by the Iowa DOT will calculate the PWL automatically using a best fit equation between QI values.

The PWL used for pay factor determination is based on a combination of the upper and lower PWLs calculated from the QI_U and QI_L . In this case the PWLs determined by the best fit equation for the QI_U (1.58) and QI_L (4.67) are 95.6 and 100.0 respectively.

Example:

$$\text{PWL} = (\text{PWL}_U + \text{PWL}_L) - 100 = (95.6 + 100.0) - 100 = 95.6$$

PWL Table for N=8 (from AASHTO R 9-97 Appendix C Table 6)

QI	PWL								
0.00	50.00	0.50	68.43	1.00	83.96	1.50	94.44	2.00	99.24
0.05	51.89	0.55	70.16	1.05	85.26	1.55	95.17	2.05	99.45
0.10	53.78	0.60	71.85	1.10	86.51	1.60	95.84	2.10	99.61
0.15	55.67	0.65	73.51	1.15	87.70	1.65	96.45	2.15	99.74
0.20	57.54	0.70	75.14	1.20	88.83	1.70	97.01	2.20	99.84
0.25	59.41	0.75	76.72	1.25	89.91	1.75	97.51	2.25	99.91
0.30	61.25	0.80	78.26	1.30	90.94	1.80	97.96	2.30	99.96
0.35	63.08	0.85	79.76	1.35	91.90	1.85	98.35	2.35	99.98
0.40	64.89	0.90	81.21	1.40	92.81	1.90	98.69	2.40	100.00
0.45	66.67	0.95	82.61	1.45	93.65	1.95	98.99	2.45	100.00

Note: For QI values less than zero, subtract the table value from 100.

The best fit equation used in the spreadsheet software to calculate the upper or lower PWL is:

$$\text{PWL} = 3E-10x^6 + 0.2019x^5 - 3E-09x^4 - 4.123x^3 - 2E-08x^2 + 37.881x + 50$$

Where: $x = QI_U$ or QI_L

QUALITY INDEX (QI) LAB VOIDS EXAMPLE:

Based on the weekly lot of HMA produced with a minimum of eight test values, determine the average and standard deviation for the air voids.

Quality Index for Air Voids Upper Limit (QI_U)

$$QI_U = \frac{(\text{Target } P_a + 1) - \text{Avg. } P_a}{\text{Std. Dev. } P_a}$$

Quality Index for Air Voids Lower Limit (QI_L)

$$QI_L = \frac{\text{Avg. } P_a - (\text{Target } P_a - 1)}{\text{Std. Dev. } P_a}$$

Using Table 6 in AASHTO R 9-97 Appendix C and a sample size of N=8 determine the upper and lower QI limits. A sample size of N=8 is always used regardless of the actual number of samples. The program provided by the Iowa DOT will calculate the PWL automatically using a best fit equation between QI values. No rounding is done until the final PWL is determined.

Example:

Given the following weekly lot air void information and a target air void of 4.0% determine the upper and lower limits for the QI for air voids: 3.1, 3.9, 4.2, 4.5, 4.5, 4.1, 4.3, 4.5

$$P_{a(\text{avg})} = \frac{3.1 + 3.9 + 4.2 + 4.5 + 4.5 + 4.1 + 4.3 + 4.5}{8} = 4.1375$$

$$\text{Std. Dev. } P_a = \sqrt{\frac{\sum (x - \bar{x})^2}{n - 1}} = \sqrt{\frac{1.55875}{8 - 1}} = 0.471888$$

$$QI_U = \frac{(4.0 + 1) - 4.1375}{0.471888} = 1.827763$$

$$QI_L = \frac{4.1375 - (4.0 - 1)}{0.471888} = 2.410528$$

DETERMINATION OF PERCENT WITHIN LIMITS (PWL)

Lab Voids

Using Table 6 from AASHTO R 9-97 Appendix C a sample size of N=8 and the Q_{LU} and Q_{LL} find the corresponding PWL for the Q_{LU} and Q_{LL} . A sample size of N=8 is always used regardless of the actual number of samples. In this case the PWLs determined by the best fit equation for the Q_{LU} and Q_{LL} are 98.2 and 100.0 respectively.

The PWL used for pay factor determination is based on a combination of the PWLs calculated from the Q_{LU} and Q_{LL} .

Example:

$$\text{PWL} = (PWL_U + PWL_L) - 100 = (98.2 + 100.0) - 100 = 98.2$$

DETERMINATION OF PAY FACTOR

The pay factor is determined from the tables in the Basis of Payment section .05 of the specification. A PWL between 80.0 and 95.0 results in a pay factor of 1.000. Equations are used to determine the pay factor for other PWL values.

Example:

Using the PWL determined above for Lab Voids of 98.2 and the specified equation for a Lab Voids PWL of 95.1 – 100.0:

Lab Voids:

$$\text{PF (Pay Factor)} = 0.0060000 \times 98.2 + 0.430 = 1.019$$

Using the PWL determined above for Field Voids of 95.6 and the specified equation for a Field Voids PWL of 95.1 – 100.0:

Field Voids:

$$\text{PF (Pay Factor)} = 0.0080000 \times 95.6 + 0.240 = 1.005$$

DETERMINING AVERAGE ABSOLUTE DEVIATION (AAD) FOR LAB VOIDS

AAD is calculated by determining the absolute difference between the target and the individual test results and then averaging those values.

Example:

Target Voids $P_a = 4.0$

Individual $P_a = 3.8, 4.2, 4.1, 3.7, 3.5$

Sample	Difference	Deviation from Target	Absolute Deviation from Target
1	(4.0 - 3.8)	0.2	0.2
2	(4.0 - 4.1)	-0.1	0.1
3	(4.0 - 4.2)	-0.2	0.2
4	(4.0 - 3.7)	0.3	0.3
5	(4.0 - 3.5)	0.5	0.5

AAD (Lab Voids)
$$= \frac{0.2 + 0.1 + 0.2 + 0.3 + 0.5}{5} = 0.3$$