

**Final Report  
for  
Iowa Highway Research Board  
Research Project HR-217**

**REDUCING  
the  
ADVERSE EFFECTS  
of  
TRANSVERSE CRACKING**

For presentation at the  
64th Annual Meeting of the  
Transportation Research Board  
Washington, D.C.  
January 1985

*Highway Division*



**Iowa Department  
of Transportation**

## DISCLAIMER

The contents of this report reflect the views of the authors and do not necessarily reflect the official views of the Iowa Department of Transportation. This report does not constitute a standard, specification or regulation.

FINAL REPORT  
FOR  
PROJECT HR-217

REDUCING THE ADVERSE EFFECTS  
OF TRANSVERSE CRACKING

BY

VERNON J. MARKS  
RESEARCH ENGINEER  
515/239-1447

AND

CHARLES L. HUISMAN  
STATE MATERIALS ENGINEER  
515/239-1452

IOWA DEPARTMENT OF TRANSPORTATION  
HIGHWAY DIVISION  
OFFICE OF MATERIALS  
AMES, IOWA 50010

JANUARY, 1985

## TABLE OF CONTENTS

Abstract . . . . .	1
Introduction . . . . .	2
Problem . . . . .	2
Objective . . . . .	3
Project Location and Design . . . . .	3
Contractor and Contractual Arrangements . . . . .	3
Research Overview . . . . .	4
Use of Another Asphalt Cement . . . . .	4
Increased Asphalt Cement Content . . . . .	6
Saw and Seal Transverse Joints . . . . .	6
Materials. . . . .	6
Construction . . . . .	7
Evaluation . . . . .	8
Post Construction Testing . . . . .	8
Periodic Field Reviews . . . . .	9
Transverse Joints . . . . .	9
Asphalt Source and Content . . . . .	10
Analysis of Extracted Asphalt Cement . . . . .	12
Discussion of Results. . . . .	12
Conclusions. . . . .	14
Recommendations . . . . .	15
Acknowledgements . . . . .	15
References . . . . .	16
Table Heads . . . . .	17
Figure Captions . . . . .	25

## ABSTRACT

This research was initiated to identify methods of reducing the occurrence of transverse cracking.

Eight (four repetitive) research sections were established to study three variations in the asphalt concrete pavement. The first variation was the comparison of a low and high temperature susceptible asphalt cement (AC) from two different sources. The second variable was to saw and seal transverse joints at spacings varying from 40 to 100 feet. The third variable was to increase the AC content in the asphalt treated base by one percent. The research sections were constructed with relatively few problems.

Crack and joint surveys have been conducted on all research sections at less than one-year intervals since construction. No cracking was identified after the first winter season. The sawed joints also remained sealed through the first winter. At an age of approximately 1-1/2 years, there was substantial cracking of the high temperature susceptible AC sections and substantial failure of the sealant material in the sawed joints. After almost four years, the asphalt pavement constructed with the high temperature susceptible AC produced a crack interval of 35 feet, the low temperature susceptible AC yielded an interval of 170 feet, and the low temperature susceptible AC with an increased AC content yielded an interval of 528 feet.

The Pen-Vis Number is an effective measure of temperature susceptibility of asphalt cements. The frequency of transverse cracking is affected by the temperature susceptibility of the AC. An increased AC content also reduces the frequency of transverse cracking.

## INTRODUCTION

Over the years there have been a number of changes in asphalt paving. Lake asphalts were used prior to 1900 when AC from refined crude oil became available. The introduction and acceptance of AC from crude oil increased the supply, but also presented many more variables in the characteristics of AC. There were substantial variations in the raw product from "heavy" to "light" crude oils. This variation in crude oils necessitated differences in the refinery process, which coupled with preferential differences, yielded a wide variation in AC.

Much of the early asphalt concrete paving in the U.S. was two to four inches thick. It has, therefore, commonly been referred to as flexible pavement and rightly so. When these pavements were subjected to heavy loads during periods of unstable subgrade conditions, the structure was inadequate and the result was failure. The design has been changed to greater thickness or full depth asphalt concrete pavements to provide more structural capacity. These full depth designs are less flexible and present problems commonly encountered in rigid pavements.

## PROBLEM

One of the most serious problems of asphalt pavements today is related to transverse cracking and subsequent crack deterioration. With the heavier vehicles, thicker sections and greater stability were needed to carry the loads without permanent distortion. These changes have produced a pavement that generally exhibits transverse cracks at a relatively uniform spacing on any individual project. The spacing is apparently dependent on many factors, but is quite related to pavement thickness.

The uniformly spaced transverse cracks do not initially present any objectionable conditions. Water movement through the cracks results in stripping of the AC. Further pumping or hydraulic pressure dislodges and expels aggregate and fine material from the crack. This action can result in a large void which, given time, will result in sloughing, producing a dip. Even though the crack itself is not detrimental, subsequent deterioration results in an unacceptable riding quality and intense maintenance. This reduces the effective life of an otherwise structurally sound roadway.

#### OBJECTIVE

The objective of this research project was to identify a method of reducing the adverse effect of transverse cracking and to improve the performance of asphalt pavement. This objective can be achieved either by reducing the occurrence of the transverse cracking or preventing deterioration of joints sawed to take the place of random cracking.

#### PROJECT LOCATION AND DESIGN

The research was incorporated into Jones County asphalt concrete paving project F-64-1(12)--20-53 on Iowa 64 from U.S. 151 (Anamosa) to the west junction of Iowa 38. This project was selected because it is typical of many Iowa primary roadways with three inches of asphalt surface over eight inches of asphalt treated base (ATB) and granular surfaced earth shoulders (Figure 1). The research section is currently (1982 data) carrying 1160 VPD with 13% trucks.

#### CONTRACTOR AND CONTRACTUAL ARRANGEMENTS

The successful bidder for the project was Cessford Construction Company of LeGrand, Iowa. The research was added by extra work order. The sawing and sealing portion of the research was subcontracted to Concrete Specialists of Cedar Rapids.

## RESEARCH OVERVIEW

The research involved three variations from the contractor's planned operation. Briefly, they were:

1. Use of another asphalt cement.
2. Saw and seal transverse joints.
3. Increased asphalt cement content.

The research was placed between the stations noted (Figure 2):

1. Sugar Creek Asphalt Cement
  - a. Stations 150+00 to 169+00
  - b. Stations 210+00 to 230+00
2. Transverse Joints
  - a. Stations 170+00 to 193+60
  - b. Stations 230+00 to 253+20

Each research section includes:

1. 15 joints at a 40' spacing
  2. 10 joints at a 60' spacing
  3. 7 joints at an 80' spacing
  4. 6 joints at a 100' spacing
3. Increased Asphalt Cement Content
    - a. Stations 193+60 to 208+50
    - b. Stations 253+20 to 270+00

### Use of Another Asphalt Cement

Substantial study of stiffness and temperature susceptibility of asphalt cements has been conducted by Norman W. McLeod (1). The results of these studies provide a quantitative number for describing the temperature susceptibility of an AC. This aspect of the research was developed to

determine if a relationship could be identified between the temperature susceptibility as determined by the Pen-Vis Number (PVN) at penetration (77°F) and viscosity (140°F) and the frequency of transverse cracking. Dr. McLeod established the PVN = 0 to represent an excellent AC with low temperature susceptibility and PVN = -1.5 to represent an AC with very high temperature susceptibility (Figure 3). Iowa DOT personnel have been determining the PVN of all asphalt cements used in Iowa in recent years by the McLeod graph. Even though it is accepted that there are probably many factors that affect the frequency of transverse cracking, a trend seemed to indicate that transverse cracking did relate to the PVN. Research was needed where all other factors were held constant.

The contractor had normally used a relatively high temperature susceptible AC meeting Iowa DOT specifications. Initial plans for the research were based on this assumption. An AC produced by Amoco Oil Company at the Wood River, Illinois, refinery was partially blown and exhibited one of the lowest temperature susceptibilities of any asphalt cement commonly used in Iowa. Plans were to require a Wood River AC in both the base and surface courses for two 2,000' sections.

Immediately following the preconstruction conference, information became available showing that due to current economic conditions, the AC in the contractor's storage was predominately the low temperature susceptible Wood River bitumen. Research plans were changed to require an AC from Amoco Oil Company of Sugar Creek, Missouri, (a high temperature susceptible AC) for two 2,000' sections in the ATB, binder and surface.

### Increased Asphalt Cement Content

The intent was to increase the asphalt cement content in the base by one percent with some increase in the binder and surface. An additional mix design for the surface was made, and the results were not favorable for increased AC content. Consequently, the AC content was increased 1% for the ATB with no increase for the binder or surface.

### Saw and Seal Transverse Joints

Transverse joints were cut in the surface at spacings of 40, 60, 80, and 100 feet. The saw cut was a nominal 1/4" wide and a minimum of 3" deep. This research is similar to earlier Minnesota research (2) except for sealing. In this research, the joints were sealed with an upgraded rubber asphalt sealant meeting Iowa DOT Standard Specification 4136.02A.

## MATERIALS

Prior to 1975, Iowa DOT specifications had required 85-100 penetration grade AC for surface courses on high traffic volume roadways. In 1975 the Iowa DOT changed to a viscosity grading specification requiring AC-10 for relatively high traffic volume surface courses and AC-20 for interstate or very high traffic surface courses. All AC for the ATB, binder and surface on this project was an AC-10 grade. The AC was predominately Wood River for the majority of the project. The PVN (Figure 3) for Wood River averaged -0.6 (Pen=100 Vis=1100). The high temperature susceptible AC was from Sugar Creek with a PVN of -1.2 (Pen=75 Vis=900). The contractor used two storage tanks at the plant site. One tank was used for Sugar Creek AC only and the other only for the predominately Wood River AC. Delivery tankers were scheduled carefully to maintain an adequate AC supply.

The ATB was a 3/4" Class I produced from 65% crushed limestone and 35% sand, both from the B. L. Anderson Quarry at Anamosa. The intended AC was 4.75% for all ATB except the two increased AC sections placed at 5.75%. The typical aggregate gradations for the ATB are shown in Table 1.

Two different mix combinations were used for the 3/4" Type B binder. Both mixes were produced from crushed limestone and sand from the B. L. Anderson Anamosa Quarry.

- (1) The strengthening and leveling binder mix was 60% crushed limestone and 40% sand with an intended AC content of 5.75%. The typical aggregate gradations for that mix are given in Table 1.
- (2) A 50% crushed limestone and 50% sand mix with an AC content of 6.25% was used for the 1-1/2" thick Type B binder course. The typical gradations for that mix are given in Table 1.

The 1/2" Type A surface mix was produced using 65% crushed limestone from the B. L. Anderson Anamosa Quarry and 35% sand from the B. L. Anderson Ivanhoe Pit in Linn County. An AC content of 6.00% was used for the 1-1/2" thick lift. The typical gradations are given in Table 2.

The filler-bitumen ratio (percentage of material passing the #200 screen divided by the percentage of AC by weight) ranged from 1.08 to 1.44 for the Type A surface.

All prime and tack coat bitumen was diluted SS1 emulsified asphalt.

#### CONSTRUCTION

Construction of the ATB began on June 16, 1980. The final lift of the asphalt concrete surface was laid on August 22, 1980. Most of the construction

operation was standard practice. All asphaltic concrete mix was produced in a Cedar Rapids batch plant located at the B. L. Anderson Anamosa Quarry.

All asphalt layers were laid full width (24' traveled roadway) with a Cedar Rapids laydown machine. A Dynapac CC 50A in the vibratory mode was used for breakdown compaction followed by intermediate compaction with a pneumatic roller and final compaction with an 8-10 ton static steel Bomag roller.

The subcontractor cut the transverse joints with a 1/4" carborundum blade without water. Initially, there were substantial problems as the cutting residue would adhere tightly to the surfaces within and adjacent to the cut. It appeared that this operation would not provide a satisfactorily clean saw cut for sealing. The subcontractor added compressed air cleaning immediately following the cutting operation and this removed the cutting residue.

An excess of sealant material was used leaving some along the joint and allowing traffic to carry some down the roadway.

Except for the changes required for the research sections, the construction problems were minimal. The general appearance of the asphalt paving in the research area was good.

## EVALUATION

### Post Construction Testing

Cores were drilled from each layer of the asphalt pavement soon after construction. Density, percent of lab density and voids were determined. For research evaluation purposes, eight (four repetitive) sections were established. Two-thousand-foot sections of standard design and construction (control section) at both ends of the research were included for comparison. A summary of the core data is given in

Table 3. The Iowa DOT laboratory density for this rural primary highway with less than 5000 VPD is determined from a 50 blow Marshall Specimen.

Two cores drilled through the asphalt pavement verified that the transverse joints were the specified nominal 1/4" width and minimum 3" depth and the sealant filled the entire saw cut. Further testing demonstrated that the sealant was bonded to both faces extremely well.

#### Periodic Field Reviews

Construction of the asphalt concrete surface was completed in August, 1980. No distress was identified in any of the research sections during the late fall and early winter of 1980. Temperatures in Iowa during the 1980-81 winter season were relatively mild.

#### Transverse Joints

All transverse joints appeared to be well sealed during a field review on January 22, 1981. They continued to provide a tight seal through October of 1981.

Iowa experienced an extended period of severely cold temperatures during the winter of 1981-82. A visual review of the joints on March 1, 1982, revealed substantial failure of the sealant material. There is a total of 76 joints and only 14 (18%) remained sealed. There were 22 (29%) with partial failure and 40 (53%) that were essentially unsealed. The bond between the sealant and the face of the saw cut failed due to the thermal contraction stress from the severe temperatures.

A survey on November 17, 1982, revealed failure of all 38 of the joints between Stations 170+00 and 193+60. The joints between Station 230+00 and 253+20 were in slightly better condition. At the time of

the survey, essentially all of the joints at 80' and 100' spacings (14 joints) had failed. Five of the ten joints at 60' had failed. Six of the fourteen joints at 40' had failed. Considering all 76 joints, 63 (83%) had failed and those at a shorter spacing were performing slightly better than the longer interval.

This difference between sections may relate to the cutting and cleaning procedure used by the subcontractor during construction. The cutting residue was more effectively expelled from the joints between 230+00 and 253+20 than those between 170+00 and 193+60.

The last survey of January 25, 1984, during another severely cold winter period, showed that essentially all joints had failed. Some of the joints that had been sawed 1/4" wide had thermal movement, leaving openings up to one inch.

There are no transverse cracks between any of the sawed transverse joints. The joints will be resealed during 1985 in an effort to prevent deterioration of the joint.

#### Asphalt Source and Content

Crack surveys have been conducted on all research sections at less than one-year intervals since construction (Table 4). No cracking was identified in any of the sections on January 22, 1981, after most of one relatively mild winter. An October 16, 1981, crack survey still did not identify any cracking.

The severely cold 1981-82 winter period did cause substantial cracking in both sections constructed with Sugar Creek AC. In March, 1982,

there was a total of 110 transverse cracks in 3900 lineal feet or an average crack interval of 35 feet. One crack occurred in the standard Wood River AC section. There were no cracks in the Wood River AC section with increased AC content in the ATB.

Visual crack surveys were made on November 17, 1982, and June 2, 1983, with no additional cracking from that noted in March, 1982. The winter of 1983-84 had an extended period of severely cold weather (-20°F) and produced additional transverse cracking. The standard Wood River AC section had a total of 22 cracks in 3740 feet. There were six cracks in the 3170-foot (two sections) of Wood River at an increased AC content for the ATB. No additional cracking was identified in the Sugar Creek AC section. The crack intervals for the three research variables 3-1/2 years after construction are:

<u>Variable</u>	<u>Crack Interval, Feet</u>
Sugar Creek AC	35
Standard Wood River AC	170
Wood River Increased AC Content	528

The rutting of all research sections was determined on November 6, 1984. Rut depths under a 4-foot straight edge were measured in all four wheelpaths. The average rut depth was:

Standard Project Construction	0.04"
Highly Temperature Susceptible AC	0.05"
Increased AC in ATB	0.10"
AC Pavement with Transverse Joints	0.07"

Analysis of Extracted Asphalt Cement

Cores were drilled from all research sections with asphalt mix variables on April 5, 1984, almost four years after construction. The penetration (77°F) and viscosity (140°F) were determined for asphalt cement extracted from various layers (Table 5). The average values were:

## Sugar Creek - Binder and Surface

Penetration	40
Viscosity	2924
PVN	-1.04

## Wood River - Binder and Surface

Penetration	55
Viscosity	2918
PVN	-0.61

## Wood River Increased AC Content - ATB

Penetration	73
Viscosity	1983
PVN	-0.55

## DISCUSSION OF RESULTS

There is no cracking between any of the transverse joints, with the longest spacing being 100 feet. This is not unexpected as the average crack interval of the comparative Wood River section is 170 feet at an age of 3-1/2 years.

At the present time, there is no apparent deterioration of the joints. There is a potential problem in that they are essentially unsealed. The cracks on this project have incurred no noticeable depressions to date. Depressions ranging from 0.1" to 0.2" have developed at the joints.

The sealant failure may have been affected by the subcontractor's difficulty in removal of the cutting residue from the dry sawing operation. Cores drilled soon after construction showed that a tight bond was achieved. After 1-1 1/2 years, the seal of many joints had failed. The section between 170+00 and 193+60 where dry cutting was initiated without immediate compressed air cleaning failed more rapidly than the 230+00 to 253+20 section with improved cleaning. This would indicate that the cutting residue affected the bond between the sealant and the asphalt concrete. If this research were repeated, wet cutting should be required. An improved high modulus sealant should be used. The joints will be resealed in an effort to prevent surface water infiltration.

This research documented the effect of some asphalt cements on the frequency of transverse cracking. The only difference between the Sugar Creek and Wood River sections was the AC source. The Sugar Creek sections exhibited severe transverse cracking at an average interval of 35 feet in less than two years while the Wood River section exhibited only one crack in 3740 feet. In 3-1/2 years the average crack interval for the Wood River section was 170 feet compared to the 35 feet for the Sugar Creek which had remained constant. There is no significant difference in rut depths of the various research sections at this time.

The average viscosities of the Sugar Creek and Wood River asphalt cements after almost four years are nearly the same with 2924 and 2918 respectively. Viscosity alone is, therefore, not a good measure of the potential of an AC to yield transverse cracking.

From this research both the penetration and the PVN of the extracted AC relate well to the frequency of transverse cracking. The penetration continues to decrease due to oxidation. In almost four years the penetration of Sugar Creek had decreased from 75 to 40 and Wood River from 100 to 55. The PVN, on the other hand, remains relatively constant as documented by Iowa DOT experience in recent years. The Sugar Creek PVN at construction was -1.2 (based on a very limited number of penetration tests) and -1.0 four years later (Figure 3). The PVN for Wood River was -0.6 both at time of construction and after four years. For this reason, it would appear that the PVN is a more desirable measure of the potential for transverse cracking.

An increased AC content in the ATB has reduced and/or retarded the incidence of transverse cracking. The average crack interval of the standard project construction with Wood River asphalt was 170 feet. An average crack interval of 528 feet was obtained with everything but the AC content remaining constant. The increased AC content resulted in a reduced ATB void content (Table 3) from an average of 11.1% for the control to 6.7% for the increased AC section. This may be a very important factor in the improved performance.

#### CONCLUSIONS

This research on transverse cracking and the temperature susceptibility of asphalt cement supports the following conclusions:

1. An improved sealant or sealing procedure is needed if transverse joints are to be used in asphalt pavements.

2. The PVN is an effective measure of the temperature susceptibility of asphalt cements.
3. The use of a high temperature susceptible asphalt cement produced severe transverse cracking.
4. The use of asphalt cements with low temperature susceptibility will reduce the frequency of transverse cracking.
5. An increased asphalt cement content in the ATB will reduce the frequency of transverse cracking.

#### RECOMMENDATIONS

Earlier Iowa DOT specifications for asphalt cement did not ensure the best possible pavement. A recommendation for an improved specification was made on the basis of this research. A change from AASHTO M226 Table 1 requirements to Table 2 requirements has been adopted for 1984 projects.

Prior to this project the AC content specified for ATB was 4.75%. Mix designs are now used to determine the AC content and limit the void content. This should yield improved performance and extended life of full depth asphalt pavements.

#### ACKNOWLEDGEMENTS

Research project HR-217 was sponsored by the Iowa Highway Research Board with Primary Road Research Funding of \$43,000. The excellent cooperation of Larry Parrott and the Cessford Construction Company personnel in constructing the special sections was appreciated.

Iowa DOT personnel William Crawford, Erv Shaffer, Raymond Ellis, and others of the Manchester Construction Residency along with Dick Merritt, Dennis Lohrer and the District 6 Materials personnel provided good inspection, monitoring, and documentation of the research. Robert Shelquist, Lowell Zearley (Office of Materials) and Don Jordison (Office of Construction) supported the research with their expertise.

#### REFERENCES

1. McLeod, N.W. "Asphalt Cement: Pen-Vis Number and It's Application to Moduli of Stiffness", ASTM Journal of Testing and Evaluation, Vol. 4, No. 4, July, 1976.
2. Morchinek, R.M., "Sawing Joints to Control Cracking in Flexible Pavement", Minnesota DOT Special Study No. 315, Progress Report - 1974.

TABLE HEADS

1. Typical Gradations for ATB and Binder Mixes
2. Typical Gradations for Type A Surface Mix
3. Core Density Summary
4. Summary of Transverse Cracking
5. Summary of Tests from Asphalt Cement Extracted from Cores Drilled  
April 5, 1984

Table 1 TYPICAL GRADATIONS FOR ATB AND BINDER MIXES

Material	Crushed		ATB	Type B	Type B
	Limestone	Sand		Binder	Binder
			65% L.S.	60% L.S.	50% L.S.
Proportions			35% Sand	40% Sand	50% Sand
Sieve					
Size					
3/4"	100		100	100	100
1/2"	84		90	90	92
3/8"	65	100	77	79	82
#4	36	98	57	60	66
#8	25	87	47	50	56
#16	19	73	38	41	46
#30	17	48	28	29	32
#50	16	15	16	16	16
#100	15	1.6	10	9.6	8.3
#200	10	0.5	6.7	6.2	5.2

Table 2 TYPICAL GRADATIONS FOR TYPE A SURFACE MIX

Sieve Size	Percent Passing		
	65% Crushed Limestone	35% Sand	Type A
1/2"	100		100
3/8"	88	100	92
#4	52	98	68
#8	32	90	52
#16	24	75	42
#30	21	46	30
#50	18	13	16
#100	16	1.6	11
#200	9.0	0.5	6.0

Table 3A

## CORE DENSITY SUMMARY

Section	Experimental Feature	Station		Course	Density	% of Lab	Voids
		from	to		gr/cm <sup>3</sup>	density	%
1A	Sugar Creek AC	150+00	169+00	ATB 1st	2.24	95.2	11.3
				ATB 2nd	2.24	96.1	11.8
				Type B	2.19	94.2	11.2
				Type A	2.29	95.4	6.6
1B	Sugar Creek AC	210+00	230+00	ATB 1st	2.28	96.1	9.8
				ATB 2nd	2.22	95.0	
				Type B	2.22	95.3	9.9
				Type A	2.32	96.7	5.4
2A	Transverse Joints	170+00	193+60	ATB 1st	2.27	96.1	10.7
				ATB 2nd	2.23	95.2	12.3
				Type B	2.25	97.0	8.9
				Type A	2.30	95.8	6.2
2B	Transverse Joints	230+00	253+20	ATB 1st	2.26	95.2	10.6
				ATB 2nd	2.30	96.8	8.3
				Type B	2.17	93.5	12.1
				Type A	2.31	95.8	6.2

Table 3B

## CORE DENSITY SUMMARY

Section	Experimental Feature	Station		Course	Density	% of Lab	Voids
		from	to		gr/cm <sup>3</sup>	density	%
3A	Increased AC	193+60	208+50	ATB 1st	2.30	95.8	6.6
				ATB 2nd	2.29	96.4	5.2
				Type B	2.22	95.7	10.1
				Type A	2.28	95.0	7.0
3B	Increased AC	253+20	270+00	ATB 1st	2.29	96.7	
				ATB 2nd	2.25	96.7	8.2
				Type B	2.20	96.6	11.1
				Type A	2.31	95.8	6.2
4A	Control	130+00	147+40	ATB 1st	2.27	96.7	9.9
				ATB 2nd	2.24	96.0	11.9
				Type B	2.21	92.1	10.2
				Type A	2.28	95.0	7.0
4B	Control	270+00	290+00	ATB 1st	2.23	96.3	11.5
				ATB 2nd	2.17	93.9	
				Type B	2.21	95.2	10.5
				Type A	2.30	95.4	6.6

Table 4 SUMMARY OF TRANSVERSE CRACKING

Research Section	Beginning Stations		Number of Cracks					
	Milepost	from to	1-22-81	10-16-81	3-1-82	11-17-82	6-2-83	1-25-84
Standard Wood River AC	2.1	130+00 147+40	0	0	1	1	1	4
	4.7	270+00 290+00	0	0	1	1	1	18
Wood River	3.3	193+60 208+50	0	0	0	0	0	1
Increased AC in the ATB	4.4	253+20 270+00	0	0	0	0	0	5
Sugar Creek AC	2.5	150+00 169+00	0	0	41	41	41	41
	3.6	210+00 230+00	0	0	69	69	69	69

Table 5A                    SUMMARY OF TESTS FROM ASPHALT CEMENT EXTRACTED  
    FROM CORES DRILLED APRIL 5, 1984

Core Number	Station	Research Section	Course	Penetration	Viscosity	PVN
3	155	Sugar Creek AC	Surface	31	3720	-1.10
			Binder	36	3320	-1.00
4	160		Surface	52	1830	-1.06
			Binder	41	2480	-1.08
7	215		Surface	35	3560	-1.00
			Binder	45	2190	-1.08
8	225		Surface	32	4210	-0.96
			Binder	<u>49</u>	<u>2080</u>	<u>-1.02</u>
<b>Sugar Creek Averages</b>				<b>40</b>	<b>2924</b>	<b>-1.04</b>


Table 5B SUMMARY OF TESTS FROM ASPHALT CEMENT EXTRACTED  
FROM CORES DRILLED APRIL 5, 1984

Core Number	Station	Research Section	Course	Penetration	Viscosity	PVN
<b>Increased AC</b>						
5	200	(Wood River)	ATB	74	1990	-0.52
6	205		ATB	66	2440	-0.48
9	260		ATB	72	1880	-0.58
10	265		ATB	<u>79</u>	<u>1620</u>	<u>-0.60</u>
<b>Increased AC Averages</b>						
<b>(Wood River)</b>				<b>73</b>	<b>1983</b>	<b>-0.55</b>
<b>Control</b>						
1	135	Control (Wood River)	Surface	45	3450	-0.68
			Binder	51	3910	-0.45
2	140		Surface	63	2090	-0.68
			Binder	65	2290	-0.56
11	275		Surface	52	3290	-0.56
			Binder	47	3460	-0.65
12	280		Surface	65	2100	-0.63
			Binder	<u>53</u>	<u>2750</u>	<u>-0.66</u>
<b>Control Averages</b>						
<b>(Wood River)</b>				<b>55</b>	<b>2918</b>	<b>-0.61</b>

FIGURE CAPTIONS

1. Typical Section
2. Schematic Layout of Asphalt Cement Sources
3. Chart for Calculating Modified Penetration Index From Penetration @ 77° F & Viscosity @ 140° F McLeod Procedure

**Figure 1**      **TYPICAL SECTION**

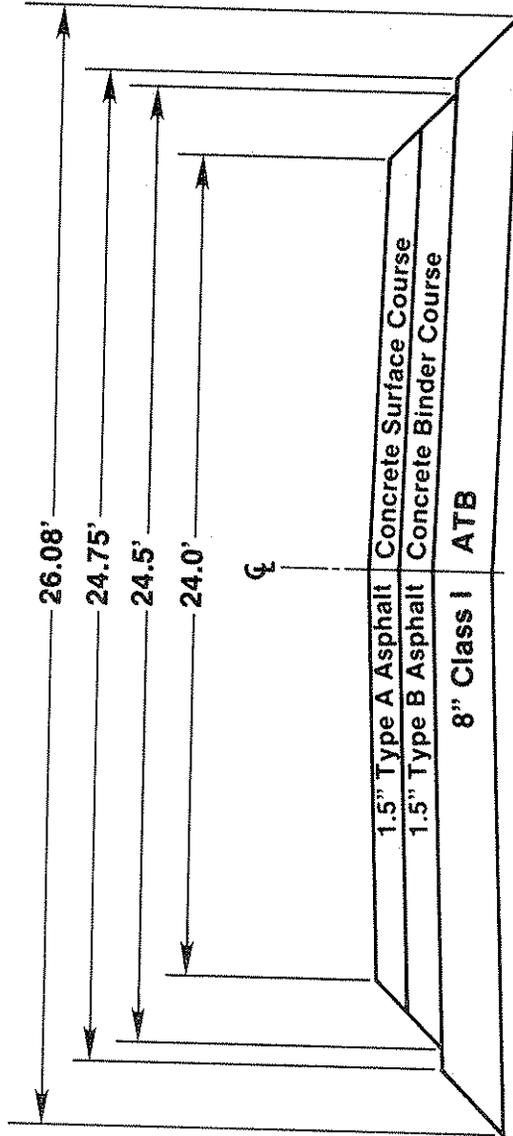

SCHEMATIC LAYOUT OF ASPHALT CEMENT SOURCES

Figure 2

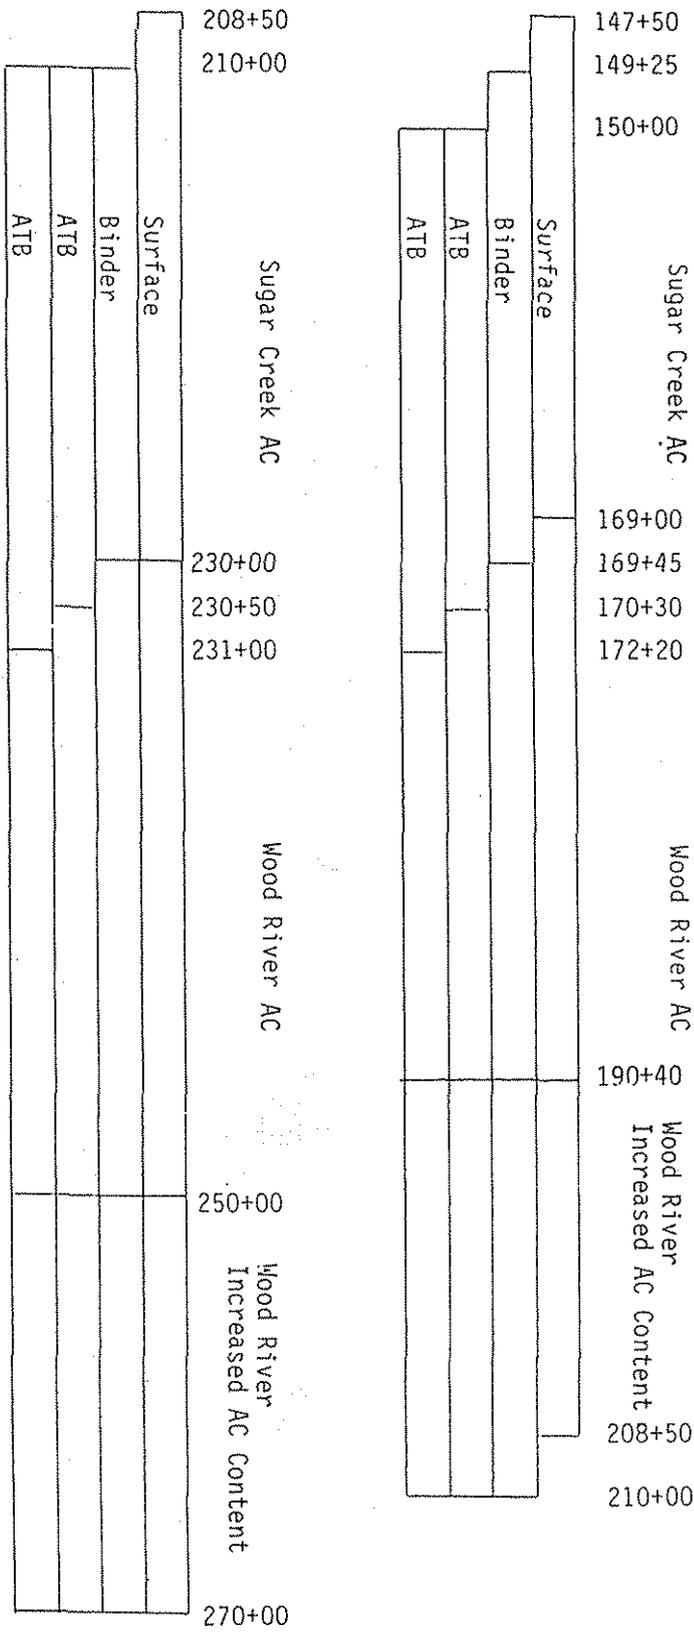


Figure 3

CHART FOR CALCULATING  
MODIFIED PENETRATION INDEX  
FROM PENETRATION @ 77°F & VISCOSITY @ 140°F  
McLEOD PROCEDURE

